

Hot Tear-Melt Quality Relationship in 3xxx Aluminium Alloys

Murat ÇOLAK

Department of Metal Education,
Faculty of Technical Education,
Sakarya University,
mcolak@sakarya.edu.tr

Engin TAN

Department of Material Science
and Engineering, Faculty of
Technology
Pamukkale University
etan@pau.edu.tr

Ramazan KAYIKCI

Department of Metallurgy and
Materials Science Engineering
Sakarya University
rkayikci@sakarya.edu.tr

Derya DIŞPINAR

Department of Metallurgy and
Materials Science Engineering
İstanbul University
deryad@sakarya.edu

Abstract:

Corrosion resistance, formability and high strength is few of the major properties that makes aluminium alloys preferred choice of material for extrusion or deep drawing processes. Particularly, buildings, windows, doors are main application areas and it is growing. Twin roll casting method is used to produce such materials. One of the common problems faced in this method is called hot tearing. The effect of alloying elements is the reason for this defect. As a result, segregation causes tear and decrease process efficiency. The economic impact is immanent. Thus, it is aimed to study the hot tear tendency of 3xxx series aluminium alloys and the effect of alloying elements will be investigated in this work.

Keywords: Hot-tear, 3xxx series, Aluminium alloys, melt quality, casting simulation.

1.Introduction

It is quite common to have defects in any sort of production methods. Hot tearing is one of the defects that occur during casting processes. The size and distribution of hot tears may be up to 30 vol % of the cast part. During solidification, certain locations on a cast part may freeze later than the surroundings. Thus, these areas will be under negative pressure due to the shrinkage. Depending on the tension generated, this remaining liquid may “tear” to form the casting defect called hot tear. Hot tears may even lead up to the distortion of the cast part. The variables that affect hot

tearing can be mainly listed as follows: composition, mould design, filling conditions, process parameters etc.

Campbell [1] pointed out that these defects were associated with hydrostatic tensions in the dendritic network. Therefore many research have been carried out by using Darcy’s Law to predict the formation of hot tear in castings [2-20]. However, hot tearing still remains a complex phenomenon. Moreover, there is no single type of a test that can measure or standardize these defects. Campbell’s model for hot tearing is given in Fig. 2.

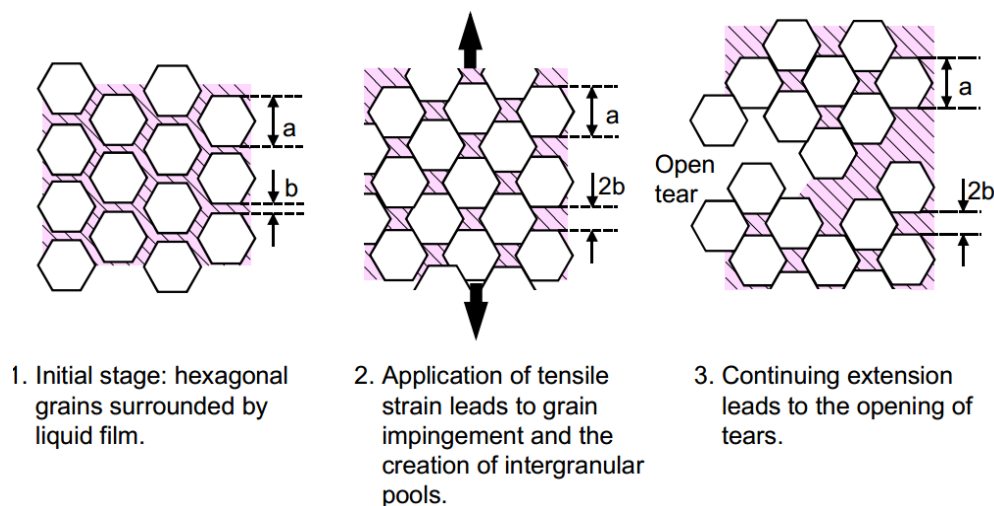


Fig. 1: A simple model of hexagonal grains of diameter “a” separated by a liquid film which initially has a thickness of “b” [1]

Therefore, in this study, two different mould designs were used to investigate the hot tearing susceptibility of 3xxx series aluminum alloys by using SolidCast simulation. The contribution of melt quality issue was also introduced into the hot tearing phenomena.

2. Experimental Work

Commercially available 3105 alloy was used to model the hot tearing susceptibility. The composition of the alloy is given in Table 1.

Table 1. Chemical Analysis of A3105 alloy

Al	Cu	Fe	Si	Zn	Mg	Mn	Ti	Cr
Balance	0,30	0,70	0,60	0,40	0,60	0,50	0,10	0,10

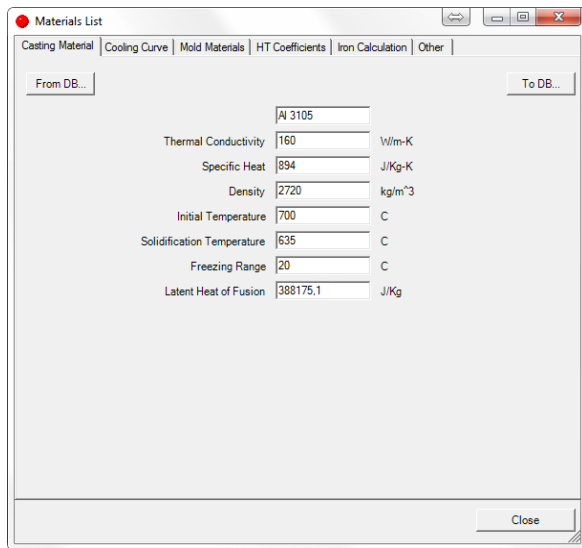


Figure 2. Parameters used in the modelling work.

For the modelling studies, two different melt temperature was selected: 700°C and 750°C; and three different mould temperatures were investigated: 20°C, 120°C and 250°C. The parameters used in the simulations are given in Fig. 2.

SolidCast software was used to simulate the casting trials. The dimension of the mould used in the simulation is given in Fig. 3. The moulds were selected to be a sand mould and a permanent mould.

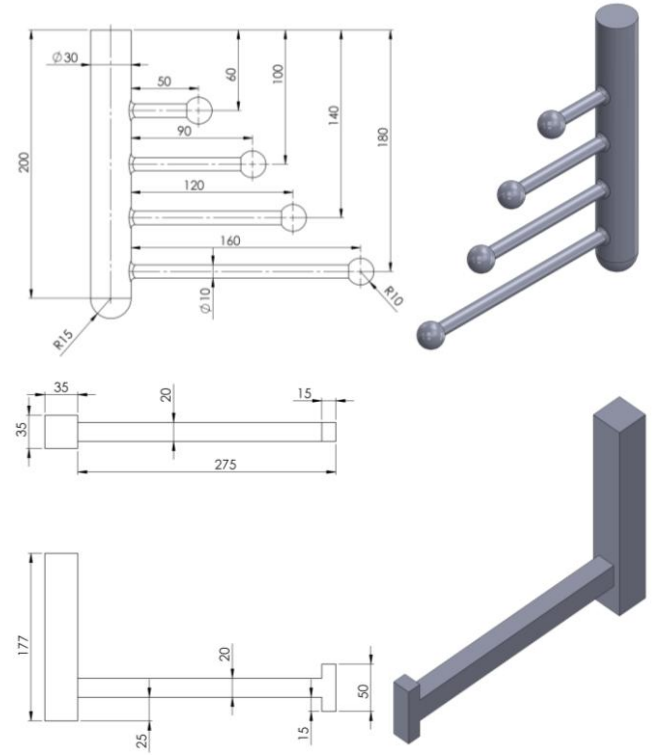



Figure 3. Dimension of the cast parts used in the modelling work.

3. Results


The simulation results that show the solidification time in the moulds are given in Table 2. The simulation results that show the hot spots in the moulds are given in Fig. 4-6.

Table 2. Solidification time results


T bone design	Solidification time(min.)	Hot tear susceptibility mould	Solidification time(min.)
Sand mould 700 °C	3.062	Sand mould 700 °C	1.895
Sand mould 750 °C	3.592	Sand mould 750 °C	2.242
Permanent mould (20°C), cast at 700°C	0.383	Permanent mould (20°C), cast at 700°C	0.287
Permanent mould (120°C), cast at 700°C	0.431	Permanent mould (120°C), cast at 700°C	0.324
Permanent mould (250°C), cast at 700°C	0.539	Permanent mould (250°C), cast at 700°C	0.405
Permanent mould (20°C), cast at 750°C	0.379	Permanent mould (20°C), cast at 750°C	0.292
Permanent mould (120°C), cast at 750°C	0.431	Permanent mould (120°C), cast at 750°C	0.337
Permanent mould (250°C), cast at 750°C	0.591	Permanent mould (250°C), cast at 750°C	0.443

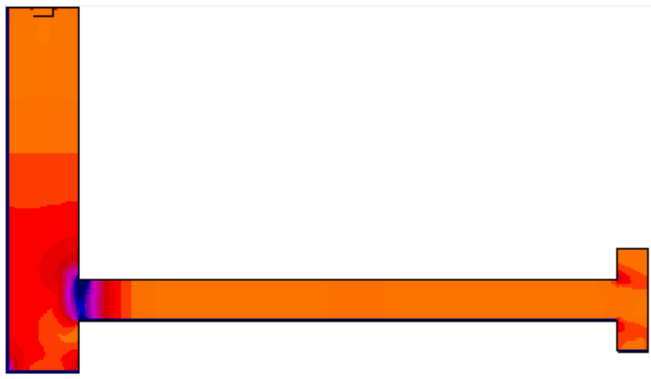

(a) Sand mould, cast at 700°C

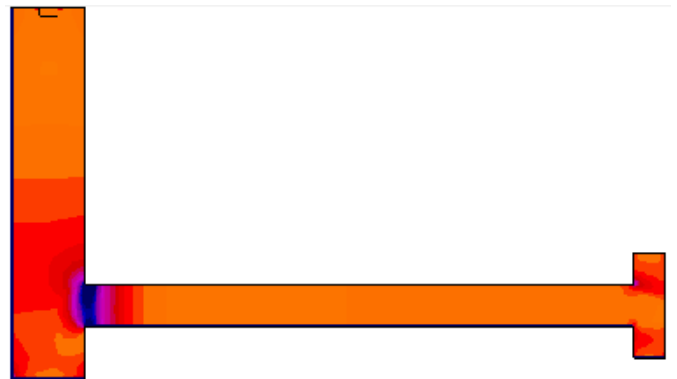


(b) Sand mould, cast at 750°C

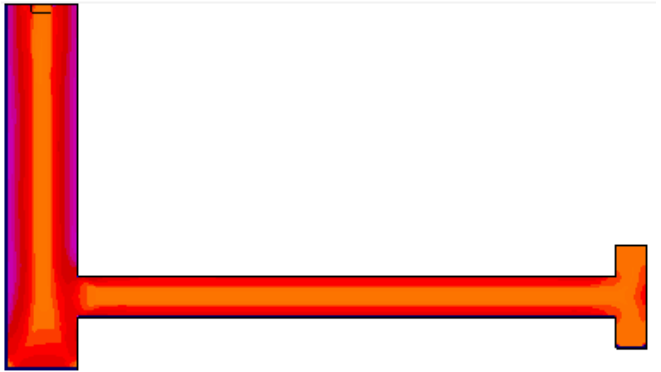

(c) Permanent mould (20°C), cast at 700°C



(d) Permanent mould (20°C), cast at 750°C

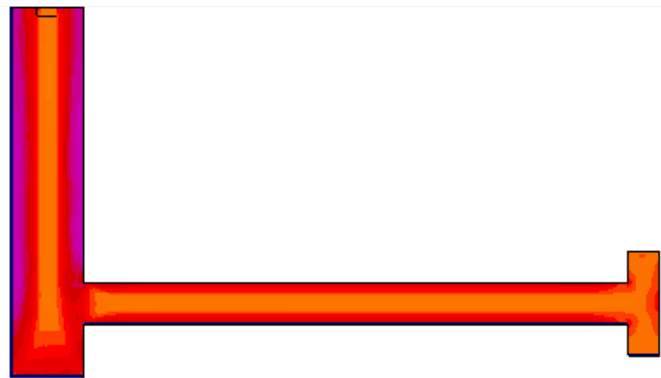

(e) Permanent mould (120°C), cast at 700°C



(f) Permanent mould (120°C), cast at 750°C




(g) Permanent mould (250°C), cast at 700°C




(h) Permanent mould (250°C), cast at 750°C


Figure 4: T-bone design simulation results

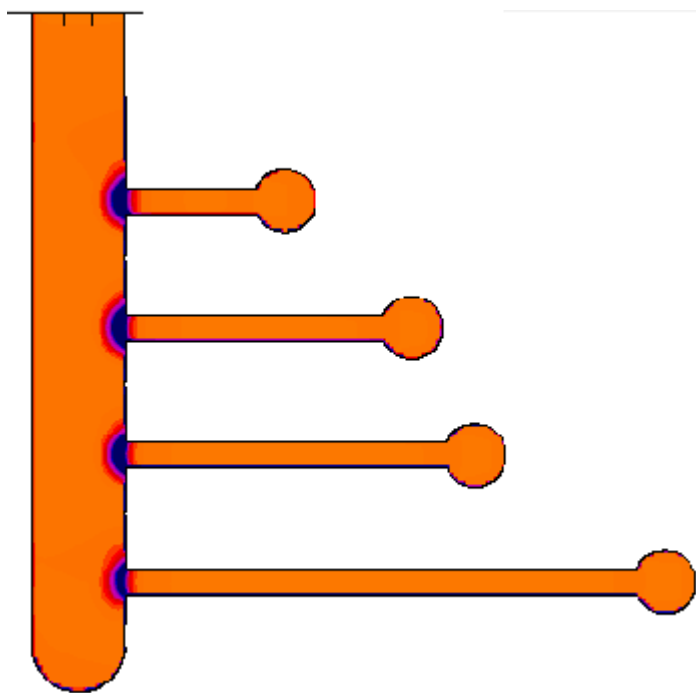


(a) Sand mould

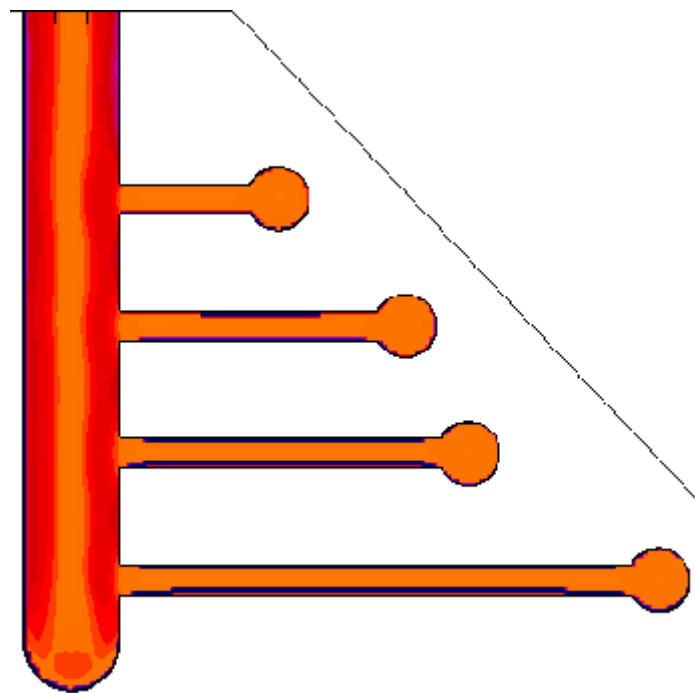

(b) Permanent mould (20°C)

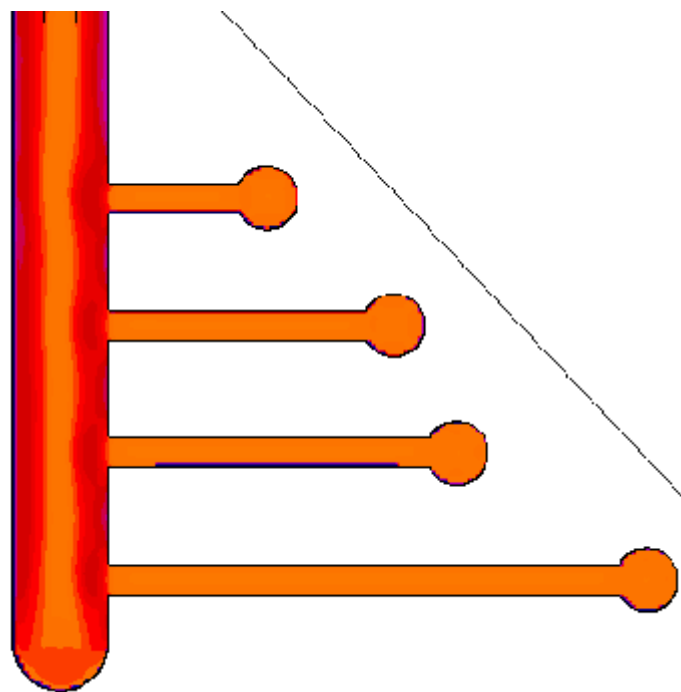


(c) Permanent mould (120°C)

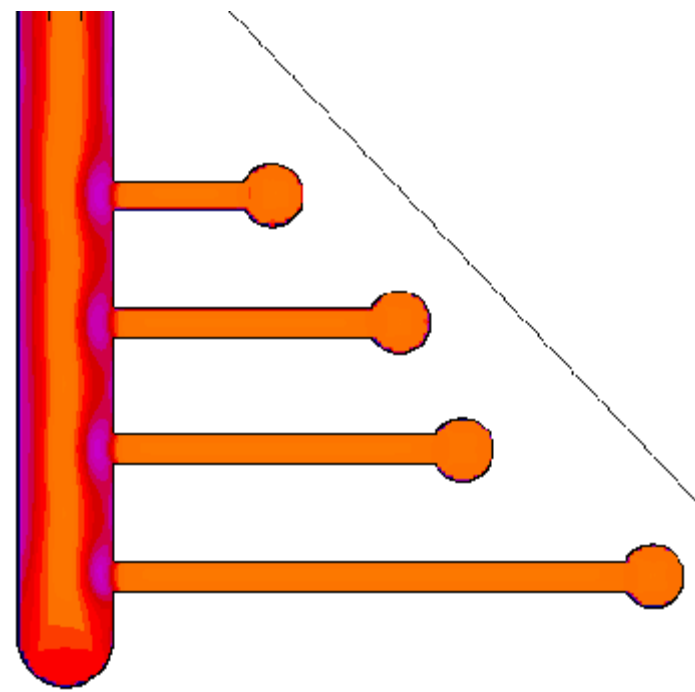


(d) Permanent mould (250°C)


Figure 5: Hot tear susceptibility mould simulation results, cast at 700°C

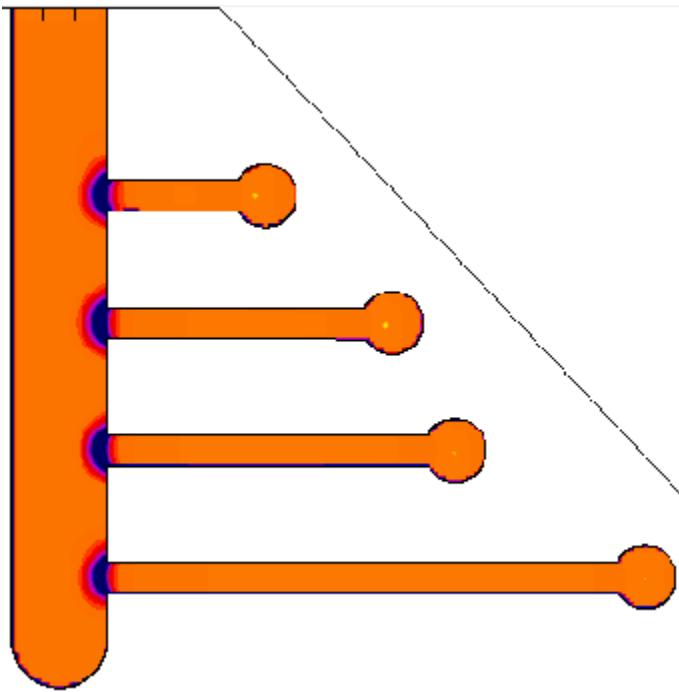


(a) Sand mould

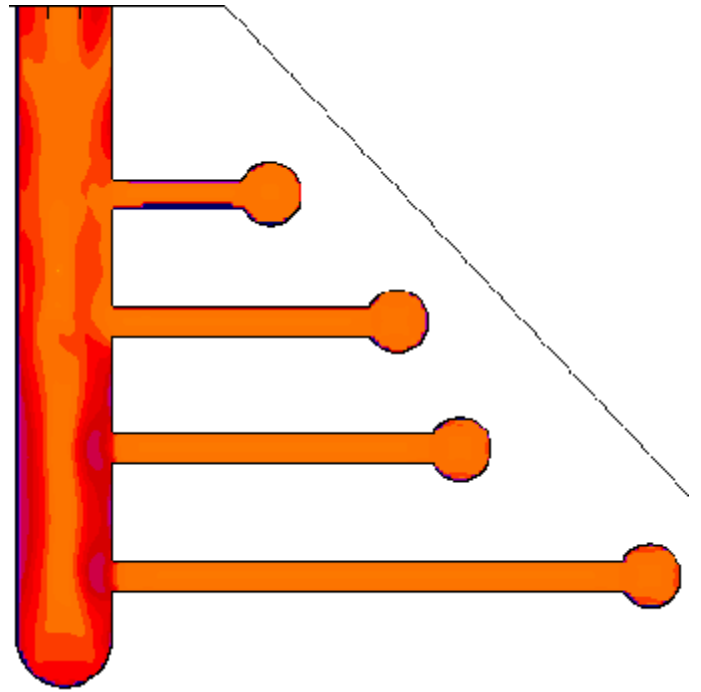

(b) Permanent mould (20°C)

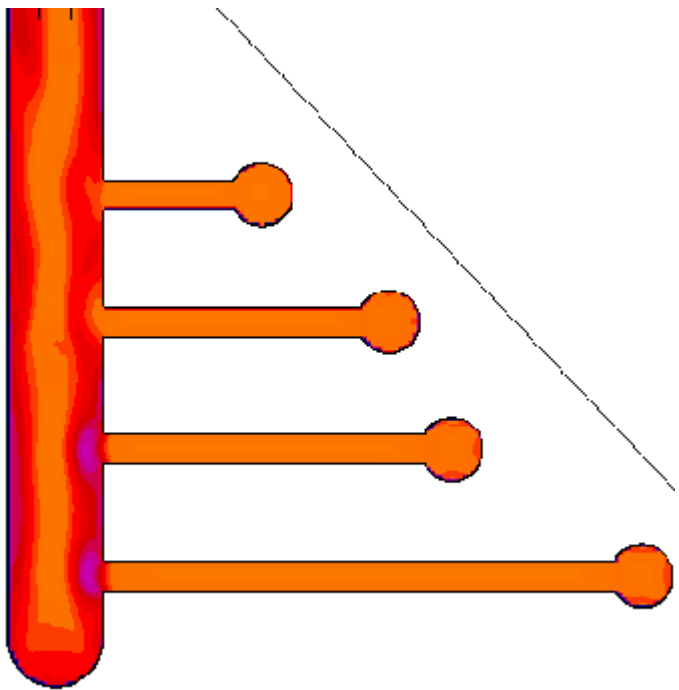

(c) Permanent mould (120°C)

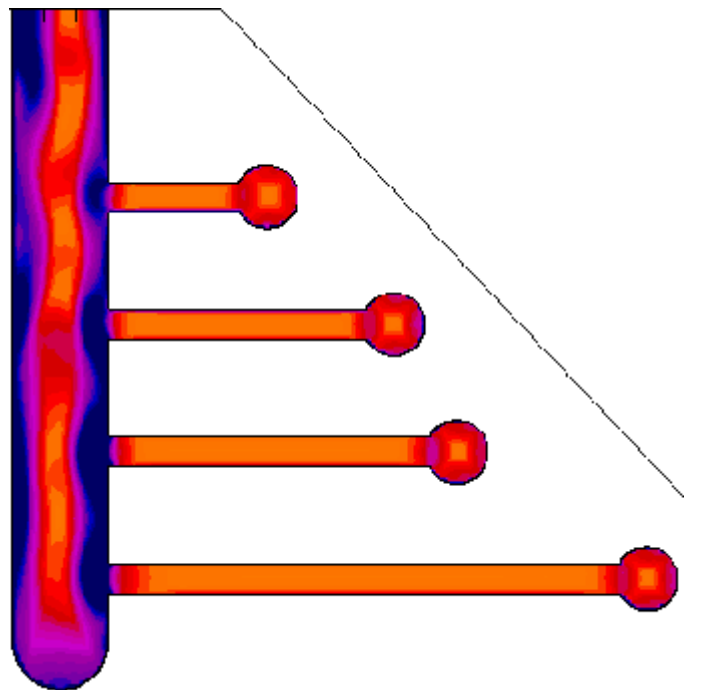

(d) Permanent mould (250°C)

Figure 6: Hot tear susceptibility mould simulation results, cast at 750°C

4. Discussion

Two of the moulds were designed such that the long and thin cross-sectioned bars would solidify earlier than the thick pouring basin. In this way, there would be a hot spot at the junction points of the bars with the runner. These predictions were verified by the simulation results shown in Figs 4-6.

Different moulds (namely: sand and permanent) were used with different casting temperatures and various mould temperature in order to investigate the hot tearing susceptibility of 3105 alloy.

Thermal strain caused by the contraction during solidification was highest in the sand mould and at the permanent mould heated to 250 °C. It has been reported that 3105 type alloys exhibit a ductile fracture depending on the dendritic network (equiaxed or columnar).

The difference between the bar mould (Fig. 2a) and T-bone (Fig. 2b) is that with the bar mould, various effects of contraction rates can be examined. However, there are more studies with the T-junction type moulds in the literature.

The simulation results show the areas of hot spots. And the proportion and the distribution of these areas gives an indication

The existing hot tearing criteria have limited applicability. It has always been assumed that for a gap between grains to open into a tear, one of two conditions is required. Either a pressure drop within the mushy zone, or grains are pulled apart and the liquid film thickness increases. In either case, the pressure difference between the local liquid and the atmosphere exceeds the capillary pressure. However, one important aspect of hot tearing is that it needs to be nucleated. Aluminium alloys are known for their protective oxides that forms on the surface of the

References

- [1] Campbell, J., *Castings*. 2003: Butterworth Heinemann.
- [2] Eskin, D.G, L. Katgerman, 2007, *A Quest for a New Hot Tearing Criterion*, Mat Trans 38A, July, 1511
- [3] Bichler, L. and C. Ravindran, *New Developments in Assessing Hot Tearing in Magnesium Alloy Castings*. Materials & Design, 2010. 31, Supplement 1(0): p. S17-S23.
- [4] Dinnis, C.M., J.A. Taylor, and A.K. Dahle, *As-cast Morphology of Iron-intermetallics in Al-Si Foundry Alloys*. Scripta Materialia, 2005. 53(8): p. 955-958.
- [5] Du, Z.-m., et al., *Tensile Properties of As-deformed 2A50 Aluminum Alloy in Semi-solid State*. Transactions of Nonferrous Metals Society of China, 2010. 20(9): p. 1597-1602.
- [6] Esfahani, M.R.N. and B. Niroumand, *Study of Hot Tearing of A206 Aluminum Alloy Using Instrumented*

melt. When this oxide is disturbed during filling (i.e. uncontrolled pouring), a detrimental defect known as bifilms may form and these may be carried into the cast part. Bifilms are in the form of folded oxide skins. Therefore there exists an unbonded gap between these defect which may be readily opened to aid hot tearing.

Hot Tearing Susceptibility (HTS) in the mould given in Fig. 2a is calculated as follows:

$$HTS = \sum [L_i \times C_i] \quad (1)$$

L_i is the length of the rod where the hot tear occurs and C_i is the severity of each tear. Severity ranges between 0-4 where 0 means no tear, 4 is the maximum tear where complete separation occur between the rod and the runner. An experimental work will be carried out to correlate melt quality with the HTS and simulation results.

4. Conclusions

Sand mould castings require chilling to eliminate hot tearing.

When permanent mould is used, the temperature of the mould play a significant role for hot tearing susceptibility. At room temperature, the feeding becomes difficult; at 250°C, sharp edges increased hot tearing susceptibility; however, 120°C appears to be an optimum temperature to eliminate hot tearing in 3105 alloy.

Simulation results are useful tool to identify the hot spots in a mould.

Further work is required to investigate the effect of melt quality and hot tearing susceptibility of aluminum castings.

Constrained T-shaped Casting Method. Materials Characterization, 2010. 61(3): p. 318-324.

- [7] Fabrègue, D., et al., *Two- and Three-dimensional Characterizations of Hot Tears in a Al-Mg-Si Alloy Laser Weld*. Scripta Materialia, 2008. 59(3): p. 324-327.
- [8] Farup, I., J.M. Drezet, and M. Rappaz, *In Situ Observation of Hot Tearing Formation in Succinonitrile-acetone*. Acta Materialia, 2001. 49(7): p. 1261-1269.
- [9] Flemings, M.C., *Solidification Processing*. 1974: McGraw-Hill.
- [10] Han, Q., et al., *Dross Formation During Remelting of Aluminum 5182 Remelt Secondary Ingot (RSI)*. Materials Science and Engineering: A, 2003. 363(1-2): p. 9-14.
- [11] Kamguo Kamga, H., et al., *Hot Tearing of Aluminum-copper B206 Alloys With Iron and Silicon Additions*. Materials Science and Engineering: A, 2010. 527(27-28): p. 7413-7423.

- [12]Kwon, Y.-D. and Z.-H. Lee, *The Effect of Grain Refining and Oxide Inclusion on the Fluidity of Al-4.5Cu-0.6Mn and A356 Alloys*. Materials Science and Engineering: A, 2003. 360(1-2): p. 372-376.
- [13]Li, M., et al., *The Effect of Y on the Hot-tearing Resistance of Al-5wt.% Cu Based Alloy*. Materials & Design, 2010. 31(5): p. 2483-2487.
- [14]M'Hamdi, M. and A. Mo, *On Modelling the Interplay Between Microporosity Formation and Hot Tearing in Aluminium Direct-chill Casting*. Materials Science and Engineering: A, 2005. 413-414(0): p. 105-108.
- [15]Phillion, A.B., S.L. Cockcroft, and P.D. Lee, *X-ray Micro-tomographic Observations of Hot Tear Damage in an Al-Mg Commercial Alloy*. Scripta Materialia, 2006. 55(5): p. 489-492.
- [16]Phillion, A.B., S.L. Cockcroft, and P.D. Lee, *A New Methodology for Measurement of Semi-solid Constitutive Behavior and its Application to Examination of As-cast Porosity and Hot Tearing in Aluminum Alloys*. Materials Science and Engineering: A, 2008. 491(1-2): p. 237-247.
- [17]Robinson, J.S., et al., *Influence of Processing on the Properties of the Aluminium Alloy 2025 with a Zirconium Addition*. Journal of Materials Processing Technology, 2009. 209(6): p. 3069-3078.
- [18]Shabestari, S.G. and S. Ghodrati, *Assessment of Modification and Formation of Intermetallic Compounds in Aluminum Alloy Using Thermal Analysis*. Materials Science and Engineering: A, 2007. 467(1-2): p. 150-158.
- [19]Suyitno, D.G. Eskin, and L. Katgerman, *Structure Observations Related to Hot Tearing of Al-Cu Billets Produced by Direct-chill Casting*. Materials Science and Engineering: A, 2006. 420(1-2): p. 1-7.
- [20]Wang, J., et al., *The Apparent Viscosity of Fine Particle Reinforced Composite Melt*. Journal of Materials Processing Technology, 2003. 136(1-3): p. 60-63.
- [21]Wang, Z., et al., *Hot Tearing Susceptibility of Binary Mg-Y Alloy Castings*. Materials & Design, 2013. 47(0): p. 90.